

Recent achievements and trends in laser welding of thin plates

D. IORDACHESCU, M. BLASCO, R. LOPEZ, A. CUESTA, M. IORDACHESCU^a, J. L. OCAÑA*

UPM Laser Centre, Polytechnical University of Madrid, Spain

^aMaterials Science Dept., ETSI Caminos, Polytechnical University of Madrid, Spain

Laser Welding (LW) is more and more chosen as manufacturing process due to its advantages, namely capability of joining small dimension parts, opportunities for joining of special materials, less Heat Affected Zone, good repeatability, high speed etc. Nowadays, LW is of particular interest in manufacturing small mechatronics parts of mechanic, electric or electronic nature. This paper underscores several achievements in three key-processes, namely classical LW, laser hybrid welding (LHW) and remote laser welding (RLW). These results were obtained at the UPM Laser Centre (CLUPM) of Polytechnical University of Madrid (Universidad Politécnica de Madrid) with a CO₂ laser of 3350 W dedicated to RLW of thin sheets for automotive and other sectors, and with a Nd:YAG laser of 3300 W, respectively. The second is operated by a 6-axis ABB robot and is meant for various laser processing methods, including welding. Several important applications experimented at CLUPM and recently implemented in industry are briefly presented: RLW of coated sheets (with Zn or Al), LW of thin sheets of stainless steel and carbon steel (dissimilar joints), LW of high strength automotive sheets, LW vs. laser hybrid welding of Double Phase steel thin sheets, LW of Shape Memory Alloys (NiTi). The way in which the team of CLUPM has addressed some knowledge gaps related to LW, LHW and RLW are underscored, together with the benefits of the new technologies for both science and industry.

(Received May 04, 2011, accepted May 11, 2011)

Keywords: Automobile industry, Manufacturing systems, Equipment, Laser welding, Coated steel sheets, Shape memory alloys, Dissimilar joints

1. Introduction

Laser technologies and laser welding started a new technological age in the last decades of the 20th century, due to clear advantages for industry, namely high precision, high productivity, flexibility and the effectiveness, assuring their effective implementation into automated manufacturing environments, as discussed by Engler (2006).

Present applications for Laser Welding (LW) include sectors such as automotive, aerospace, defense, marine and ship building, medical, electronics, power generation and networks, chemical industry, alternative energy (fuel cells, solar power and wind turbines), nuclear, oil and gas, on- and off- highway transportation equipment, as well as home appliances. E.g., analyzing integral shell designs for aerospace structures, it results that laser beam welding could reduce manufacturing cost due to automation, less material consumed for joining and sealing, fewer production steps, and improved corrosion behavior, as presented by Southwell et al. (2006).

Similar and dissimilar joints of wide arrays of materials are possible to be achieved by LW, including high strength steels, high carbon alloy steels, stainless steels, cast irons, aluminum alloys, nickel-based alloys, titanium, and plastics.

The continuous need of increasing manufacturing effectiveness has determined rapid changes in terms of equipment, technologies and processes. E.g., remote laser welding (RLW) is replacing more and more the resistance

spot welding in automotive and home appliances manufacturing.

Beside the classical LW, this paper addresses actual key-processes, namely RLW and laser hybrid welding (LHW), together with several correspondent applications in the field of laser welding of thin sheets of special steels, developed in UPM Laser Centre (CLUPM).

2. Remote laser welding

The LW process characterized by increased values of focal length (long standoff), when the laser beam is long-distance focused in the joint plane by means of two-axis mirror(s) system, is usually referred as Remote Laser Welding (RLW).

Remote laser beam delivery, either through optical fiber or a guiding optical path, is gaining interest as an emerging technique for the welding of coated steel sheets in the automotive, home appliances and other mass-production industries in view of its versatility and amenability to high production throughput.

Typical RLW systems with long focal length (1.2-2.0 m) have the structure as described in Fig. 1, a working volume as shown in Fig. 2 (is the case of the RLW cell at CLUPM) and are usually equipped with CO₂ lasers about 3.5-6 kW and higher (Herfurth et al., 2005).

Remote welding of Zn-coated steel sheets under optically guided slab CO₂ laser beam has been shown to be feasible for typical car body construction materials and overlap joints up to 5 mm total thickness. This method is used in the practice of the automotive plants to weld up to four overlapped thin Zn-coated plates and replaces more and more the classical resistance spot welding.

3.2 RLW of aluminum-coated thin steel sheets

RLW process is highly feasible for other special steels used in automotive and other industries, such as double-phase high strength (DP, DX, DOCOL etc.). An example of RLW joint of high strength steel Aluminum-coated sheets (USIBOR coated with ALUSI: 91% Al + 9% Si), is presented in Fig. 4.

In this case, the issue is created by the numerous types of aluminum inter-metallic compounds which may appear in the weld, decreasing its strength. The main advantages of USIBOR are the very high strength ($R_m = 1,500$ MPa) obtained after hot stamping, as well as the high formability due to the same process. The ALUSI coating is compatible with the hot stamping process and assures a very good corrosion protection. The welding process must damage as less as possible the aluminum protection.

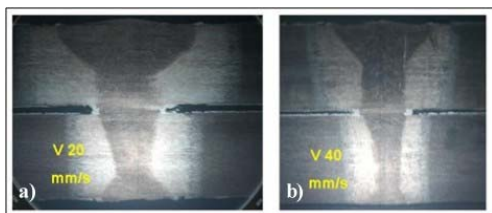


Fig. 4. RLW joints welded with CO₂ laser at CLUPM: USIBOR 1500+ALUSI, defect-free welds achieved at two welding speeds (20 and 40 mm/s), keyhole mode.

There are also several concerns related to overlap and patch welding, such as the negative influence of the coating on the weldability, or the measures necessary to keep the mechanical (static and dynamic) properties obtained after thermal treatment. USIBOR may be welded coated or uncoated, but it is complicate and costly to achieve the coating after welding. On the other hand, welding may be achieved before hardening by hot plastic deformation, or after. In the latter case, the welding thermal cycle must not decrease the mechanical properties of the treated USIBOR.

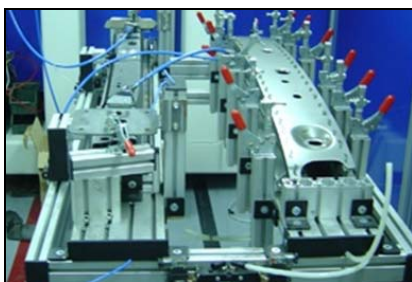


Fig. 5. Experimental setup at CLUPM for testing RLW technologies for joining a Ford Focus part.

The high speed (about 60 stitches of 5 mm length each in about 1 min, Fig. 5), accurate positioning and easy access to any point inside the working volume makes RLW a serious industrial option for mass production.

4. Nd:YAG laser welding

4.1 Nd:YAG laser welding of thin sheets

In the robotized LW facility at CLUPM, the laser beam is transported by optical fiber from the Nd:YAG of 3300W maximum power laser equipment to the ABB 6-axis robot, equipped with the welding head corresponding to the chosen technique. Fig. 6a shows the robot operating a laser head with a focal distance of 250 mm assuring a minimum spot diameter of 0.5 mm.



Fig. 6. ABB robot operating a Nd:YAG laser beam at CLUPM for: a. laser welding b. laser hybrid welding.

If appropriate devices are used, thin sheets starting from 0.35 mm can be successfully welded. Good welds were obtained for shape-memory alloys NiTi sheets of 0.5 mm (Alberty et al, 2010), and also when welding stainless steel thin plates. Fig. 7a shows quality butt welded joints made of AISI 304 stainless steel of 0.5 mm, whilst Fig. 7b presents an overlap welded joint of the same plates.

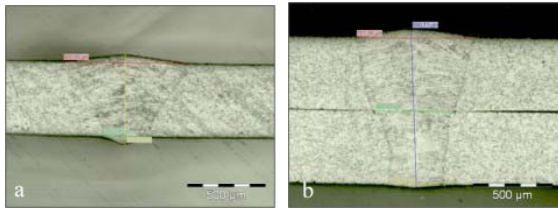


Fig. 7. LW of AISI 304 stainless steel of 0.5 mm at CLUPM: a. transition from conduction to keyhole mode welding; b. keyhole mode welding.

Fig. 7 illustrates the different techniques used for laser welding in these two cases; this makes laser welding a versatile method, allowing welding by conduction, transition (Fig 7a), or keyhole mode (Fig 7b).

Usual LW is not using filler material. Fig 8 shows welded joints of galvanized DP 1000 steel without filler material – basic LW. If using Laser Hybrid Welding, filler material is used together with the GMAW process (Fig. 9).

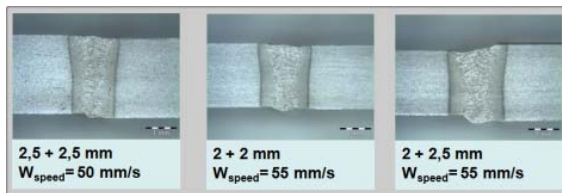


Fig. 8. LW joints of DP 1000 steel sheets without filler material, using LW in keyhole mode at CLUPM.

4.2 Laser hybrid welding of thin sheets dissimilar joints

Important development of Laser Hybrid Welding (LHW) was noticed in the last decade in industrial applications in shipbuilding, automotive, aircraft and other industries. This generic name and concept is widely understood as combination of two classic processes: GMAW and Laser Welding (LW), respectively. Fig. 6b presents the Laser Hybrid Welding head operational at CLUPM.



Fig. 9. LHW joints of DP 1000 steel sheets with filler material using LHW in keyhole mode at CLUPM.

As a holistic approach, LHW is meant to bring mainly low heat input, low deformation, better metallurgical quality, higher welding speed, low distortion, higher bridgeability, and lower spattering.

The process allows the design of the material constitution in the weld, which is highly requested especially when welding different material, to achieve quality dissimilar joints (Iordachescu, D., 2011). E.g., in case of stainless steel-carbon steel dissimilar joints (Ferritic-Austenitic, also called “Black and White”), the main issue to overcome is the formation of deleterious

constitutions, that occurs if the chemical composition is not strictly controlled. This is possible by choosing the appropriate filler material and controlling the heat input in each plate (Iordachescu, M., 2010).

5. Conclusions

Time savings, flexibility enhancement and design possibilities that RLW offers are threshold references for nowadays industrial manufacturing.

Further LHW development can address welding of dissimilar joints, allowing a good prediction and control of the heat input and apportionment in each plate. This also opens a challenging new topic in fracture mechanics and complex characterization of heterogeneous medium.

Acknowledgments

The authors gratefully acknowledge the partial financial support of the projects FIT-020600-2004-74, FIT-020600-2005-52 and EUREKA E! 3209.

References

- [1] L. Alberty Vieira, R. M. Miranda, F. M. Braz Fernandes, J. L. Ocaña, D. Iordachescu, R. J. C. Silva, K. K. Mahesh, L. Quintino, The 63rd Annual Assembly of the International Institute of Welding, Com. IV, IIW Doc. IV-1018-10, Turkey, 2010.
- [2] A. Engler, Laser Welding in Sheet Metal Manufacturing. TRUMPF Laser Technology Centre, original internet broadcast, 26 Sept., 2006.
- [3] H. J. Herfurth, S. Heinemann, Proc. of Automotive Laser Application Workshop (ALAW), USA, 2005.
- [4] D. Iordachescu, J. L. Ocaña, M. Blasco, International Institute of Welding, Com. IV+XII, IIW Doc. IV-925-07, Spain, 2007.
- [5] D. Iordachescu, E. Scutelnicu, M. Iordachescu, A. Valiente, J. Ruiz-Hervias, J. L. Ocaña, Welding in the World, 3-4, 02-11, 2011.
- [6] M. Iordachescu, D. Iordachescu, E. Scutelnicu, J. Ruiz-Hervias, A. Valiente, L. Caballero, Science and Technology of Welding and Joining **15**(5), 378 (2010).
- [7] J. L. Ocaña, D. Iordachescu, M. Blasco, M. Iordachescu, Metalurgia International **14**(10), 10 (2009).
- [8] W. Rath, Proc. of the Third International WLT-Conference on Lasers in Manufacturing 2005, Germany.
- [9] I. S. Southwell, R. Kloczkowski, <http://www.thefabricator.com>, The fabricator®, 7 March, 2006.

*Corresponding author: jlocana@etsii.upm.es